

1           **An Evaluation of Components Manufactured from a Range of**  
2  
3           **Materials, Fabricated Using PolyJet Technology**  
4

5  
6           Nigel J. Kent<sup>a,b,\*</sup>, Lina Jolivet<sup>a,c</sup>, Paul O'Neill<sup>a</sup>, Dermot Brabazon<sup>a</sup>  
7

8  
9           <sup>a</sup>*Advanced Processing Technology Research Centre, Dublin City University, Ireland.*  
10

11  
12           <sup>b</sup>*School of Mechanical and Design Engineering, Dublin Institute of Technology.*  
13

14  
15           <sup>c</sup>*Institut National des Sciences Appliquées de Lyon, France.*  
16

17  
18           Corresponding author\*:  
19

20           Dr. Nigel Kent.  
21           Rm387,  
22           Dublin Institute of Technology,  
23           Bolton St,  
24           Dublin 1.  
25           Tel: +353 1 402 3885  
26           Email: nigel.kent@dit.ie  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

# An Evaluation of Components Manufactured from a Range of Materials, Fabricated Using PolyJet Technology.

With advances in additive manufacturing, particularly in the area of three dimensional (3D) printing, it is becoming possible to generate small quantities of functional components. As with all manufacturing technologies, the ability to reproducibly generate parts with defined dimensional accuracy and surface finish is of key importance. This work characterises the ability of one such technology, PolyJet 3D printing, to produce such parts. In order to characterise the output from the manufacturing technique, a test part was designed and manufactured in three alternative materials representative of alternative grades across a commercial range. The designed test part consisted of positive and negative feature types printed both in the direction of, and normal to, the print head traverse direction. The test parts were characterised in terms of dimensional accuracy in three dimensions and also in terms of surface finish. Differences in dimensional accuracy and surface profile were observed depending on the orientation of the feature relative to the print head travel direction.

Keywords: PolyJet; 3D printing; Additive manufacturing; Photopolymer; Inkjetting.

## Introduction.

Additive manufacturing (AM) is an umbrella term encompassing a range of manufacturing techniques that build a given 3D part in layer by layer fashion [1]. Among these additive manufacturing techniques, 3D printing is perhaps the most ubiquitous. 3D printing techniques have traditionally been used for applications in rapid prototyping at the preliminary stage of the product design life cycle. In this context, mechanical characteristics such as load bearing ability, dimensional accuracy, and build speed are not critical to the overall part production. However, recently, and in parallel with improvements in 3D printing technologies, 3D printed parts are increasingly being used as functional components for applications in low-volume high-value industries such as aerospace, automotive, tooling, jewellery, dentistry, and audiology [2]. With the

1 move toward higher volume functional components, the requirements of both  
2 processing technologies and material properties have become more stringent [3].  
3

4 From a processing technologies perspective, among the main challenges are both  
5 surface finish and dimensional accuracy of manufactured components. Given that a  
6 unique feature of 3D printing is the promise of rapidly customisable parts [3], for  
7 example, for personalised medical implants, it is of critical importance that any chosen  
8 manufacturing technology has the resolution to achieve required tolerances on  
9 dimensional accuracy and surface finish.  
10  
11  
12  
13  
14  
15  
16  
17

18 Among the current commercially available processing technologies  
19 photopolymer based inkjet printers show significant promise in terms of build speed and  
20 resolution [4]. The principle of the PolyJet 3D printing technique is depicted in Figure 1.  
21 Figure 1 (A) illustrates a print head traversing across the printer bed in the 'x' direction,  
22 as indicated in Figure. 1. The print head selectively jets a layer of photo-curable  
23 polymer (shown in yellow Figure 1 (A)) onto the print bed. This layer is then partially  
24 cured through irradiation with an ultraviolet light source (shown in Figure 1(B)). The  
25 print bed is then translated in the 'z' direction as indicated in Figure 1 and the process of  
26 deposition of another layer is repeated. Where hollow parts or overhangs are required,  
27 the print head deposits a layer of removable gel-like support material that does not  
28 crosslink with the main build material.  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44

45 The principle of PolyJet printing borrows heavily from the ink jet printing  
46 industry, as such the enabling technology is already, to a large extent, well established.  
47 As a corollary of the capacity for inkjet printing to print multiple colours, PolyJet 3D  
48 printing is among the few methods of 3D printing capable of printing multiple materials  
49 in a single build. Using PolyJet technology, single parts can be produced with a  
50 combination of alternative materials including combinations of thermoset and  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 elastomeric materials. Further, fully cured models can be handled and used  
2 immediately, without additional post-curing.  
3

4           Parts created using 3D technologies are, by the nature of the process, anisotropic  
5 [5–9]. Based on this anisotropy, the orientation of a given part relative to the traversing  
6 nature of both the print head and the printer bed may affect the quality of the finished  
7 part or key features of a given part.  
8  
9

10           The effect of build direction/orientation in the PolyJet process has been studied  
11 previously in respect to tensile stress [8, 10–13], surface roughness [8, 14], hardness  
12 [13], viscoelasticity [15], and thermomechanical properties [16]. This paper investigates  
13 the effect of build orientation on dimensional accuracy and surface finish of a given part  
14 using a commercially available PolyJet based printer, the Objet 260 Connex1 from  
15 Stratasys. The Objet260 Connex1 is a compact, entry level edition of Objet’s pioneering  
16 line of multi-material 3D printers. The printer has the capacity to print 14 alternative  
17 materials and up to 3 alternative materials in a single build. In terms of technical  
18 specifications in relation to build quality, there is no discernible difference between the  
19 Connex1 and other machines the Objet260 Connex range. As such the Objet 260  
20 Connex 1 represents an ideal test bed for investigations into processing capabilities of  
21 PolyJet technologies.  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44

## 45 **Materials and Methods**

### 46 *Test Piece.*

47  
48 In order to assess the dimensional accuracy and quality of surface finish of the Objet  
49 260 Connex 1, a test part was designed. This test part contained positive and negative  
50 features types; both in the direction of, and normal to, the print head traversing direction  
51 could be interrogated. The designed part is shown in Figure 2. A similar test piece  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 incorporating positive and negative features was used by Shallan et al. [17] to assess the  
2 dimensional accuracy of their stereolithography (SL) 3D printer (MiiCraft, Taiwan).  
3  
4 The test piece, shown in Figure 2, consists of a 30mm x 30mm x 2mm cuboid part  
5 containing pairs of features printed normal to, and in the direction of, the print head  
6 traversing direction. These features were designed to be 1mm x 10mm in the horizontal  
7 plane. Each feature pair consists of a feature protruding from the surface (positive  
8 feature) and a feature inset into the surface (negative feature) as indicated in Figure 2.  
9  
10 The feature height and depths are +500 $\mu$ m and -500 $\mu$ m respectively. Also shown in  
11 Figure 2 is a 15mm x 10mm area where surface profile measurements can be carried out  
12 across multiple locations.  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22

23  
24 The test parts were generated in SolidWORKS 2014-2015 and saved in  
25 'Stereolithographic' STL format for subsequent transfer to an Objet 260 Connex1  
26 commercial 3D printer from Stratasys. STL files are generated by tessellating the  
27 surface of the specified part into a series of small triangles. The STL file format is the  
28 conventional file format used for 3D printing. On saving the part, custom STL  
29 parameters were used in an effort to enhance part quality. The 'deviation' parameter  
30 used to control whole part tessellation, influencing whole part accuracy, was changed  
31 from 0.02mm to 0.0025mm. The 'angle' parameter, influencing smaller detail  
32 tessellation was modified from 10deg to 0.5 deg. These modifications, representing the  
33 best available through SolidWORKS, had the net effect of significantly increasing the  
34 file size for the parts, typically on the order of a ten-fold increase. These modifications  
35 had a negligible effect on actual build times of the parts.  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55

56 In total, three materials were tested [18,19]:  
57  
58  
59  
60  
61  
62  
63  
64  
65

- Vero White RGD835 is among the more established PolyJet materials and is closely aligned to Acrylonitrile Butadiene Styrene (ABS) and High-Impact Polystyrene (HIPS) in terms of properties. Vero White RGD835 falls into the Stratasys ‘standard category’ of plastics.
- High Temp RGD 525 has a higher glass transition temperature (65 deg C) than other PolyJet materials. This can be further increased through post processing heat treatment. High Temp RGD 525 is a member of the Stratasys ‘engineering plastics’ family.
- Clear Bio-compatible MED610 is a relatively new PolyJet material and was evaluated for biocompatibility in accordance with standard DIN EN ISO 10993-1: 2009, Biological Evaluation of Medical Devices-Part 1: Evaluation and testing within a risk management process.

For each material, four parts were printed during a single production run. Post processing of the parts included a high pressure water wash using a Genie400 encapsulated washing and finishing system. This wash was followed by cleaning in a 1% (<sup>w/v</sup>) NaOH solution as per the manufacturer recommendations to remove any support material. The post processed parts were subsequently tested in terms of dimensional accuracy and roughness.

### ***Dimensional Measurements.***

Dimensional accuracy of the test parts was interrogated using a Keyence 3D Digital Microscope (VHX2000E). The VHX Series Digital Microscope which has an increased depth of field and longer working distances than traditional optical microscopes allowing for the generation of surface three dimensional profiles to an accuracy of up to +/- 1µm, depending on the magnification used. In terms of Keyence settings, the images

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

were acquired using a x200 magnification giving a field of view, for a single image of 1620 x 1240 $\mu$ m. The sample was illuminated using a combination of direct and transmitted light. This combination of illumination had the net result of enhancing the contrast of the image, without impacting adversely on the integrity of the dimensional measurement.

In order to interrogate each feature pair, at multiple locations, an entire three dimensional profile of each feature pair was generated using a stitching function within the Keyence VHX2000E software. This stitching function allows a number of images taken from adjacent areas of a given part to be combined (stitched) together to generate a larger image, more representative of the overall area of interest. Sample images taken from the Keyence 3D microscope are shown in Figure 3(A). Once the image has been acquired line profiles are taken across the image to determine a two dimensional profile across the part (Figure 3(B)). Three line profiles were taken for each feature pair.

### ***Roughness Measurements.***

Roughness measurements were carried out using a WYKO NT1100 white light interferometer from Veeco and interrogated using Gwyddion data visualisation and analysis software. In a similar manner to dimension testing, averaged line profiles of roughness were taken normal to and along the direction of printing for comparison. Further, given the anisotropic nature of the part as a result of manufacturing process, the waviness of the part was measured normal to, and in the direction of, printing.

Acquired images were 736 x 480 pixels in dimension corresponding to a real world area of 2.444 x 1.859 mm. For each part three locations were interrogated. Preprocessing of the images consisted of utilising the leveling and zero fixing functions within Gwyddion. Levelling interrogates each pixel and auto determines if an inclined plane exists within the image. Given a small incline is often present due to the focusing

1 requirements of white light interferometry the leveling feature is used to compensate for  
2 any potential incline. The zero fixing function simply offsets the image such that the  
3 minimum pixel value is set to zero. While not necessary for relative measurements  
4 across a given image, the zero fixing is a useful feature when comparing absolute values  
5 across images.  
6  
7  
8  
9  
10

11 Figure 4 illustrates a typical captured image and accompanying measurements  
12 for a single location on a given part. The captured image shown top left of Figure 4,  
13 represents the raw image data acquired from the WYKO white light interferometer. The  
14 red areas shown, represent null or unrecorded data. These null data points are typically  
15 on the order of 2-5% of the overall image (3.2% in the case of Figure 4) and are ignored  
16 for all measurements. In order to overcome small areas of null data, and to obtain a  
17 more representative measure of the surface, profiles A-C are average values over a band  
18 of width 30 pixels.  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30

31 As a direct result of the manufacturing process, namely interference between  
32 adjacent print jets along the print head, a pseudo sinusoidal surface profile running  
33 normal to the print head traverse direction is produced for all parts. This periodic effect  
34 can be seen from the raw 'Texture' profile shown in Profile A (Figure 4). This profile is  
35 in contrast to those shown in Profiles B and C where no periodic nature is observed and  
36 peak to peak magnitude of the measured profiles is less than that observed for Profile A.  
37  
38  
39  
40  
41  
42  
43  
44  
45

46 In an effort to characterise this periodic effect, for each profile taken, measures  
47 of roughness (Ra) and waviness (Wa) were recorded. In effect, a filter was applied to  
48 the Texture data (black line) shown in Figure 4. The low frequency component, termed  
49 waviness (shown in red), can be considered as the overall surface profile and the high  
50 frequency component (shown in green) can be considered as roughness of the part. The  
51 distinction between the two terms can be readily observed from Profile A shown in  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Figure 4. Roughness profiles were also captured along the valley (Profile B) and peaks (Profile C) of the wave nature of the surface in an effort to ascertain if any differences in roughness occur between valleys and peaks of the surface. In total, three measurements were taken along each direction, on each part, across all four parts in each material.

## Results

### *Dimensional Accuracy.*

Figure 5 shows the mean and standard deviation for dimensional depth and height profiling for each of the three materials. Figure 5(a) shows the measured height for positive features printed in the direction of print and normal to the direction of print. Figure 5(b) shows measured depth measurements for negative features types printed in the direction of print and normal to the direction of print. The desired depth/height is of each feature is 500 $\mu\text{m}$ , as indicated by the dashed line. While the negative features are in agreement with the designed part depth, the positive features, independent of feature orientation relative to the traversing of the print head, are less than the desired height of 500 $\mu\text{m}$ . This deviation from the desired height is on the order of 3-7.5 % across all materials. This could, at least in part, be attributed to the viscous nature of the photopolymer. As each layer of a given positive feature type is printed, there is potential for the partially cured photopolymer to flow across the surface of the part, resulting in reduction in the original layer thickness. This effect, compounded layer on layer, could potentially result in a measurable reduction in desired feature height.

While the accuracy of the feature depth/height appears independent of the orientation of the feature relative to the print head traverse direction, the same cannot be said for feature width measurements. Figure 6 shows the mean and standard deviations

1 of measured widths for positive and negative features aligned with print head traverse  
2 direction, and normal to print head traverse direction in all three test materials. The  
3  
4 graphs demonstrate the impact of the print direction on the lateral dimensional accuracy  
5  
6 of a given feature. Of particular note are the data from negative feature types, printed  
7  
8 normal to the direction of print (Figure 6 (c)). The mean error between measured and  
9  
10 desired width ranges from approx. 7 – 14%.  
11  
12  
13  
14  
15

### 16 ***Roughness Measurements.***

17  
18 Figure 7 shows the mean and standard deviation of both roughness and waviness values  
19  
20 for all three materials as measured along selected line profiles previously described.  
21  
22 Across all materials the highest roughness occurred along the valley of the wave profile  
23  
24 generated as a result of the manufacturing process. The roughness values for profiles  
25  
26 taken normal to print head traverse direction and along the peak of the wave profile  
27  
28 generated were comparable in the case of MED60 and RGD525. However, in the case  
29  
30 of Vero White the roughness along the peak of the wave profile was comparable to that  
31  
32 along the valley of the wave. This is in contrast to MED610 and RGD525, the reasons  
33  
34 for this are unclear. Across all materials and directions characterised, the measured  
35  
36 values of roughness range from approximately 0.2 – 0.45  $\mu\text{m}$  and compare favourably  
37  
38 with previously published data for alternative materials using PolyJet technology [14].  
39  
40  
41  
42  
43  
44

45 In terms of waviness, the waviness values normal to the print head traverse  
46  
47 direction significantly exceed those waviness values measured along the print head  
48  
49 traverse direction. Comparing all material graphs in Figure 7 it can be seen the  
50  
51 characteristic surface feature normal to the print head traverse direction is waviness.  
52  
53 While the nature of the waviness can be attributed to the manufacturing technique, it  
54  
55 remains a defining surface feature and may be a consideration when producing parts  
56  
57 using PolyJet technology.  
58  
59  
60  
61  
62  
63  
64  
65

## Discussion

1  
2  
3 In terms of dimensional accuracy of a given part, it was found that both the orientation  
4  
5 of the part relative to the print head traverse direction and also the nature of the features  
6  
7 printed, be they in the positive or negative feature types, play an important role in  
8  
9 determining the dimensional accuracy of the features.  
10

11  
12 In terms of feature depth/height, the orientation of a feature relative to the  
13  
14 traverse direction of the print head proved significantly less important than the positive  
15  
16 or negative nature of the feature. For both orientations of the feature, it was found that  
17  
18 the positive feature height was lower, across all materials, than specified in the original  
19  
20 design. It should be noted that based on the manufacturers specifications, the Objet 260  
21  
22 Connex 1 is capable of printing minimum layer thickness, of 16  $\mu\text{m}$  [10]. Based on this  
23  
24 value it can be considered there is good agreement between desired and actual  
25  
26 dimensions for the negative features. However, in the case of positive features, the  
27  
28 measured height was in all cases greater than 16  $\mu\text{m}$  from the desired height.  
29  
30 Considering that both positive and negative feature types were printed as part of the  
31  
32 same production run, and given the accuracy of the negative feature depth, the observed  
33  
34 discrepancy between measured and desired feature height could potentially be  
35  
36 addressed from a software/firmware perspective.  
37  
38  
39  
40  
41  
42  
43

44 It was found for optimal lateral dimensional accuracy the key dimension of a  
45  
46 given feature should be placed normal to the direction of traverse of the print head. If  
47  
48 this orientation is maintained, the nature of the feature in terms of whether the feature is  
49  
50 positive or negative becomes less relevant. However, for many practical parts there may  
51  
52 be a number of key features in various directions requiring stringent dimensional  
53  
54 tolerances so this constraint may not be feasible.  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

For feature types with a key dimension along the direction of traverse of the print head, positive features were, in general, found to be smaller than designed while negative features were, for all materials tested, found to exceed the designed dimension. In relation to the manufacturers specifications, Stratasys indicate an accuracy of 20-85 $\mu$ m for feature sizes below 50mm [20]. Based on the manufacturer specifications, the MED 610 material can be considered to be within specification for all feature types and orientations measured. However, in the case of negative features printed normal to the traverse direction of the print head, the mean values of Vero White and RGD 525 were found to be outside the maximum described 85  $\mu$ m tolerance by 49  $\mu$ m and 57  $\mu$ m respectively. These values represent deviations from the manufacturer's specification on the order of 50%.

26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

In terms of surface profile, the waviness surface characteristic is a direct result of the manufacturing process and the waviness runs normal to the print head traverse direction. The roughness of the part varies between wave peak and wave trough. However, for many engineering applications sub-micron Ra values are often acceptable. Further, in terms of the use of PolyJet printing for the manufacture of functional components, many manufacturing processes, for example casting, often require some level of post processing of parts. Should either the dimensional accuracy or surface profile of a given part not be acceptable for a given application, there is potential for PolyJet printing to be used in conjunction with a more traditional, typically subtractive, manufacturing technique to further improve the part quality in terms of its physical appearance. Given the similarities of all results across all three material types measured in this work, the limitations of dimensional accuracy and surface profile can be largely attributed to the limitations of the process hardware and software as opposed to inherent limitations of the materials themselves. Given the trend in increased precision in

1 instrumentation at reducing costs, there is scope for further improvements using the  
2 underlying principle of PolyJet technology.  
3

4           Dimensional accuracy depends largely on the speed of polymerisation and the  
5 viscosity of the photocurable resin material. In the case of the Objet Connex, the time  
6 between ink-jetting and curing steps determines the level of resin relaxation/leakage  
7 with longer times leading to a reduction in dimensional accuracy. This can be mitigated  
8 by using the gel-like support material to contain the uncured resin material between ink  
9 jetting and curing steps, using the “matt” surface setting. This was not investigated in  
10 this work but preliminary data suggests that this is the case.  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21

## 22 **Conclusion**

23 This paper describes the potential of a high end commercially available additive  
24 manufacturing machine (Objet 260 Connex1) to produce functional parts. The paper  
25 focussed on the current capabilities of existing hardware as opposed to the theoretical  
26 potential of the additive manufacturing technique. Three alternative materials across the  
27 product range were tested in terms of dimensional accuracy and surface finish.  
28  
29  
30

31 Particular attention was given to the build orientation of the parts. It was found that  
32 build orientation can have a significant impact on the dimensional accuracy of features  
33 contained within a part and this trend was observed across all materials. Further, in  
34 terms of surface profiling, the dominant waviness feature of the surface is as a direct  
35 result of the nature of the manufacturing process.  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49

50           However, results across all materials tested were relatively consistent. This  
51 indicates the current limiting factor for the Objet 260 Connex 1 lies within the machine  
52 hardware/software as opposed to the materials themselves. While the dimensional  
53 accuracy and surface profiles may be acceptable for certain applications, it would be  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

expected that any improvements in the Objet range of machines would results in improvements on the dimensional accuracy and surface finish of printed parts.

## References

- [1] ASTM F2792-12a, Standard Terminology for Additive Manufacturing Technologies, ASTM International, West Conshohocken, PA, 2012, [www.astm.org](http://www.astm.org), DOI: 10.1520/F2792-12A
- [2] Y. Huang, M. C. Leu, J. Mazumder, and A. Donmez, “Additive Manufacturing: Current State, Future Potential, Gaps and Needs, and Recommendations,” *J. Manuf. Sci. Eng.*, vol. 137, no. 1, p. 14001, Feb. 2015.
- [3] N. Hopkinson and P. Dicknes, “Analysis of rapid manufacturing—using layer manufacturing processes for production,” *Proc. Inst. Mech. Eng. Part C J. Mech. Eng. Sci.*, vol. 217, no. 1, pp. 31–39, Jan. 2003.
- [4] M. Javaid, L. Kumar, A. Haleem, and V. Kumar, “Product Design and Development using Polyjet Rapid Prototyping Technology,” *Control Theory Informatics*, vol. 5, no. 3, pp. 12–20, 2015.
- [5] N. Meisel and C. Williams, “An Investigation of Key Design for Additive Manufacturing Constraints in Multimaterial Three-Dimensional Printing,” *J. Mech. Des.*, vol. 137, no. 11, p. 111406, Oct. 2015.
- [6] M. Monzón, Z. Ortega, A. Hernández, R. Paz, and F. Ortega, “Anisotropy of Photopolymer Parts Made by Digital Light Processing,” *Materials (Basel)*, vol. 10, no. 1, p. 64, 2017.
- [7] Y. Huang, M. C. Leu, J. Mazumder, and A. Donmez, “Additive Manufacturing: Current State, Future Potential, Gaps and Needs, and Recommendations,” *J. Manuf. Sci. Eng.*, vol. 137, no. 1, p. 14001, Nov. 2014.
- [8] A. Cazon, P. Morer, and L. Matey, “PolyJet technology for product prototyping: Tensile strength and surface roughness properties,” *Proc. Inst. Mech. Eng. Part B J. Eng. Manuf.*, vol. 228, no. 12, pp. 1664–1675, 2014.
- [9] N. Guo and M. C. Leu, “Additive manufacturing: technology, applications and research needs,” *Front. Mech. Eng.*, vol. 8, no. 3, pp. 215–243, Sep. 2013.
- [10] S. Adamczak, J. Bochnia, and B. Kaczmarek, “Estimating the uncertainty of tensile strength measurement for a photocured material produced by additive manufacturing,” *Metrol. Meas. Syst.*, vol. 21, no. 3, pp. 553–560, 2014.

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
- [11] M. Sugavaneswaran and G. Arumaikkannu, “Modelling for randomly oriented multi material additive manufacturing component and its fabrication,” *Mater. Des.*, vol. 54, pp. 779–785, 2014.
  - [12] J. Mueller, K. Shea, and C. Daraio, “Mechanical properties of parts fabricated with inkjet 3D printing through efficient experimental design,” *Mater. Des.*, vol. 86, pp. 902–912, 2015.
  - [13] A. Keszy and J. Kotlinski, “Mechanical properties of parts produced by using polymer jetting technology,” *Arch. Civ. Mech. Eng.*, vol. 10, no. 3, pp. 37–50, Jan. 2010.
  - [14] R. Udriou and L. A. Mihail, “Experimental determination of surface roughness of parts obtained by rapid prototyping,” *Proc. 8th WSEAS Int. Conf. Circuits, Syst. Electron. Control Signal Process.*, pp. 283–286, 2009.
  - [15] D. Blanco, P. Fernandez, and A. Noriega, “Nonisotropic experimental characterization of the relaxation modulus for PolyJet manufactured parts,” *J. Mater. Res.*, vol. 29, no. 17, pp. 1876–1882, 2014.
  - [16] T. Tábi, N. K. Kovács, I. E. Sajó, T. Czigány, S. Hajba, and J. G. Kovács, “Comparison of thermal, mechanical and thermomechanical properties of poly(lactic acid) injection-molded into epoxy-based Rapid Prototyped (PolyJet) and conventional steel mold,” *J. Therm. Anal. Calorim.*, vol. 123, no. 1, pp. 349–361, 2016.
  - [17] A. I. Shallan, P. Smejkal, M. Corban, R. M. Guijt, and M. C. Breadmore, “Cost-Effective Three-Dimensional Printing of Visibly Transparent Microchips within Minutes,” *Anal. Chem.*, vol. 86, no. 6, pp. 3124–3130, Mar. 2014.
  - [18] Stratasys, PolyJet Materials Data Sheet [Online], Available: [http://usglobalimages.stratasys.com/Main/Files/Material\\_Spec\\_Sheets/MSS\\_PJ\\_PJMaterialsDataSheet.pdf?v=635785205440671440](http://usglobalimages.stratasys.com/Main/Files/Material_Spec_Sheets/MSS_PJ_PJMaterialsDataSheet.pdf?v=635785205440671440) (accessed 13 Feb 2017)
  - [19] Stratasys, Bio-compatible “3D print Medical Devices” [Online], Available: <http://www.stratasys.com/materials/polyjet/bio-compatible> (accessed 13 Feb 2017)
  - [20] Stratasys, Objet260 Connex1 Specifications, Available: [http://usglobalimages.stratasys.com/Main/Files/Machine\\_Spec\\_Sheets/PSS\\_PJ\\_Obj260Connex1.pdf](http://usglobalimages.stratasys.com/Main/Files/Machine_Spec_Sheets/PSS_PJ_Obj260Connex1.pdf) (accessed 13 Feb 2017)

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Figure 1. The PolyJet 3D printing technique. Liquid photopolymer and support material are deposited on to the printer bed (A) and subsequently cured using an ultraviolet (UV) lamp (B).

Figure 1. Test part used in the evaluation of the Objet 260 Connex 1. Piece consists of positive and negative feature types, normal to and aligned with print head direction along with an area for surface profile measurement.

Figure 2. Stitched images and corresponding data from the Keyence VHX2000E. Stitched images are shown in 3D and plan view with indicative line profiles (A). A sample line profile used to determine dimensional integrity of the test piece (B).

Figure 4. Image acquired using WYKO NT1100 and corresponding line profiles taken at various locations across the part represented by Profiles A-C. The raw 'Texture' data shown in black, consists of a Waviness profile (red plot) and surface roughness (green plot).

Figure 5. Measured height and depth profiles for positive and negative feature types, printed in all materials. Figure 5 (a) shows height profiles for features printed normal to, and aligned with, the traverse direction of the print head. Depth profiles for features printed normal to, and aligned with, are shown in Figure 5(b). The dashed line on both figures indicates the height/depth set point.

Figure 6. Plots showing the mean and standard deviation of widths of positive and negative feature types printed normal to, and in the direction of print head traverse direction. Figure 6 (a-b) shows results from positive feature types normal to, and aligned with the direction of traverse of the print head respectively. Results from negative feature types normal to, and aligned with the direction of traverse of the print head are shown in Figure 6 (c-d). The dashed line represents the dimensional set point.

Figure 7. Measured roughness ( $R_a$ ) and waviness ( $W_a$ ) values for each material measured normal to the print head traverse direction (Normal). Valley and Peak measurements represent measurements taken along the direction of print head travel. Valley measurements as shown represent measured values along the valley of the wave. Peak profile measurements are taken along the peak of the wave profile.



Figure 1

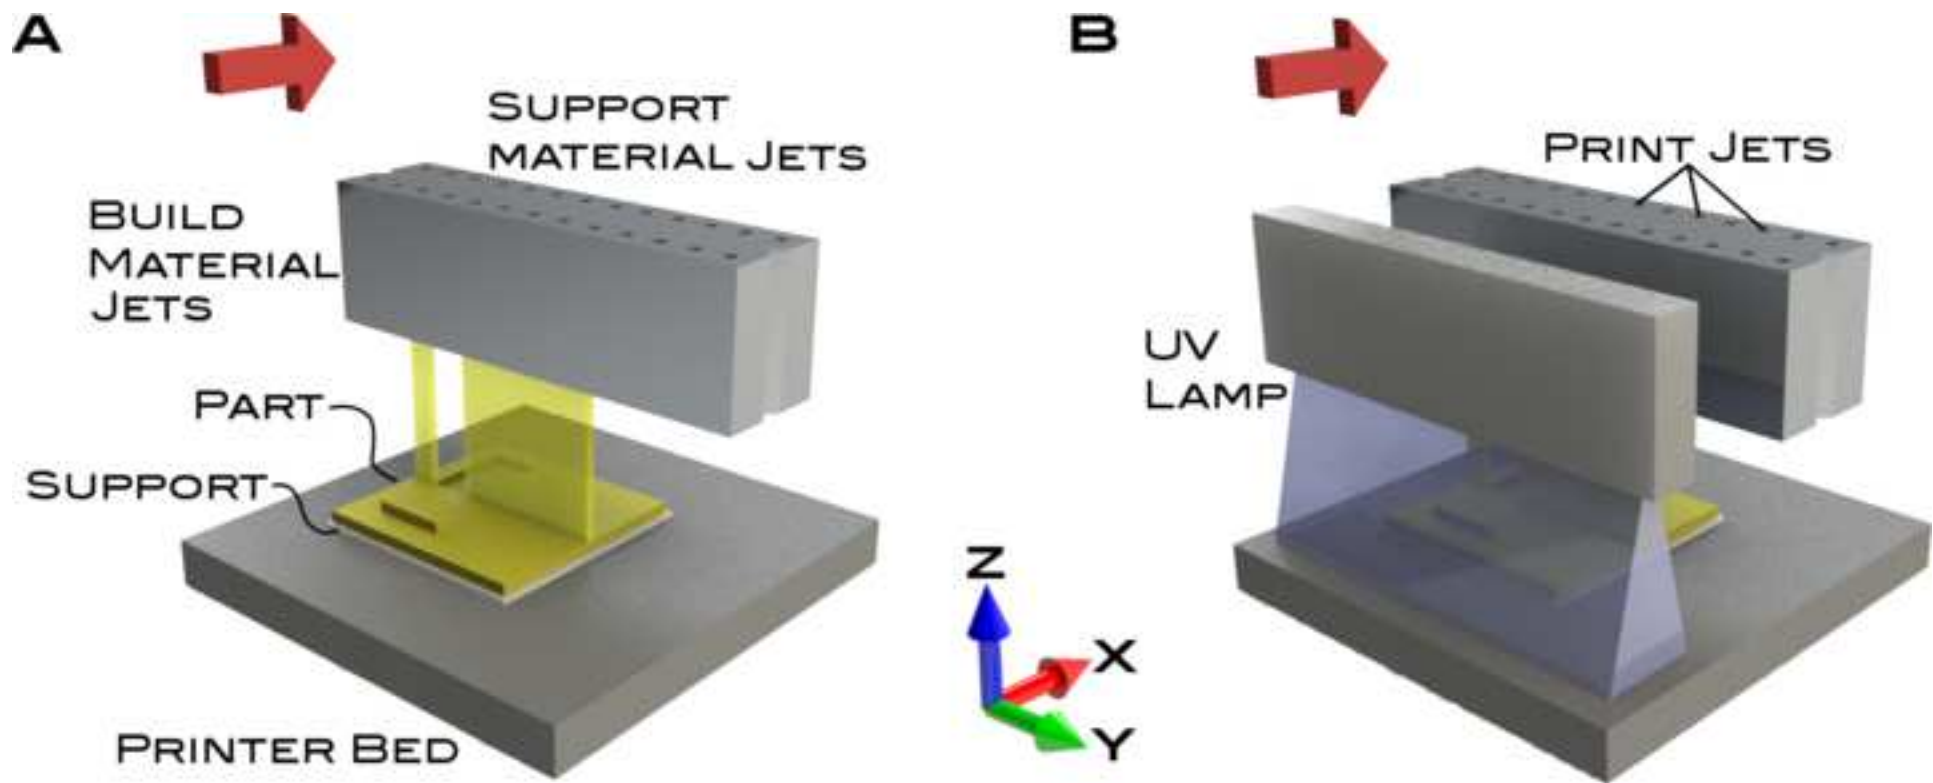


Figure 2

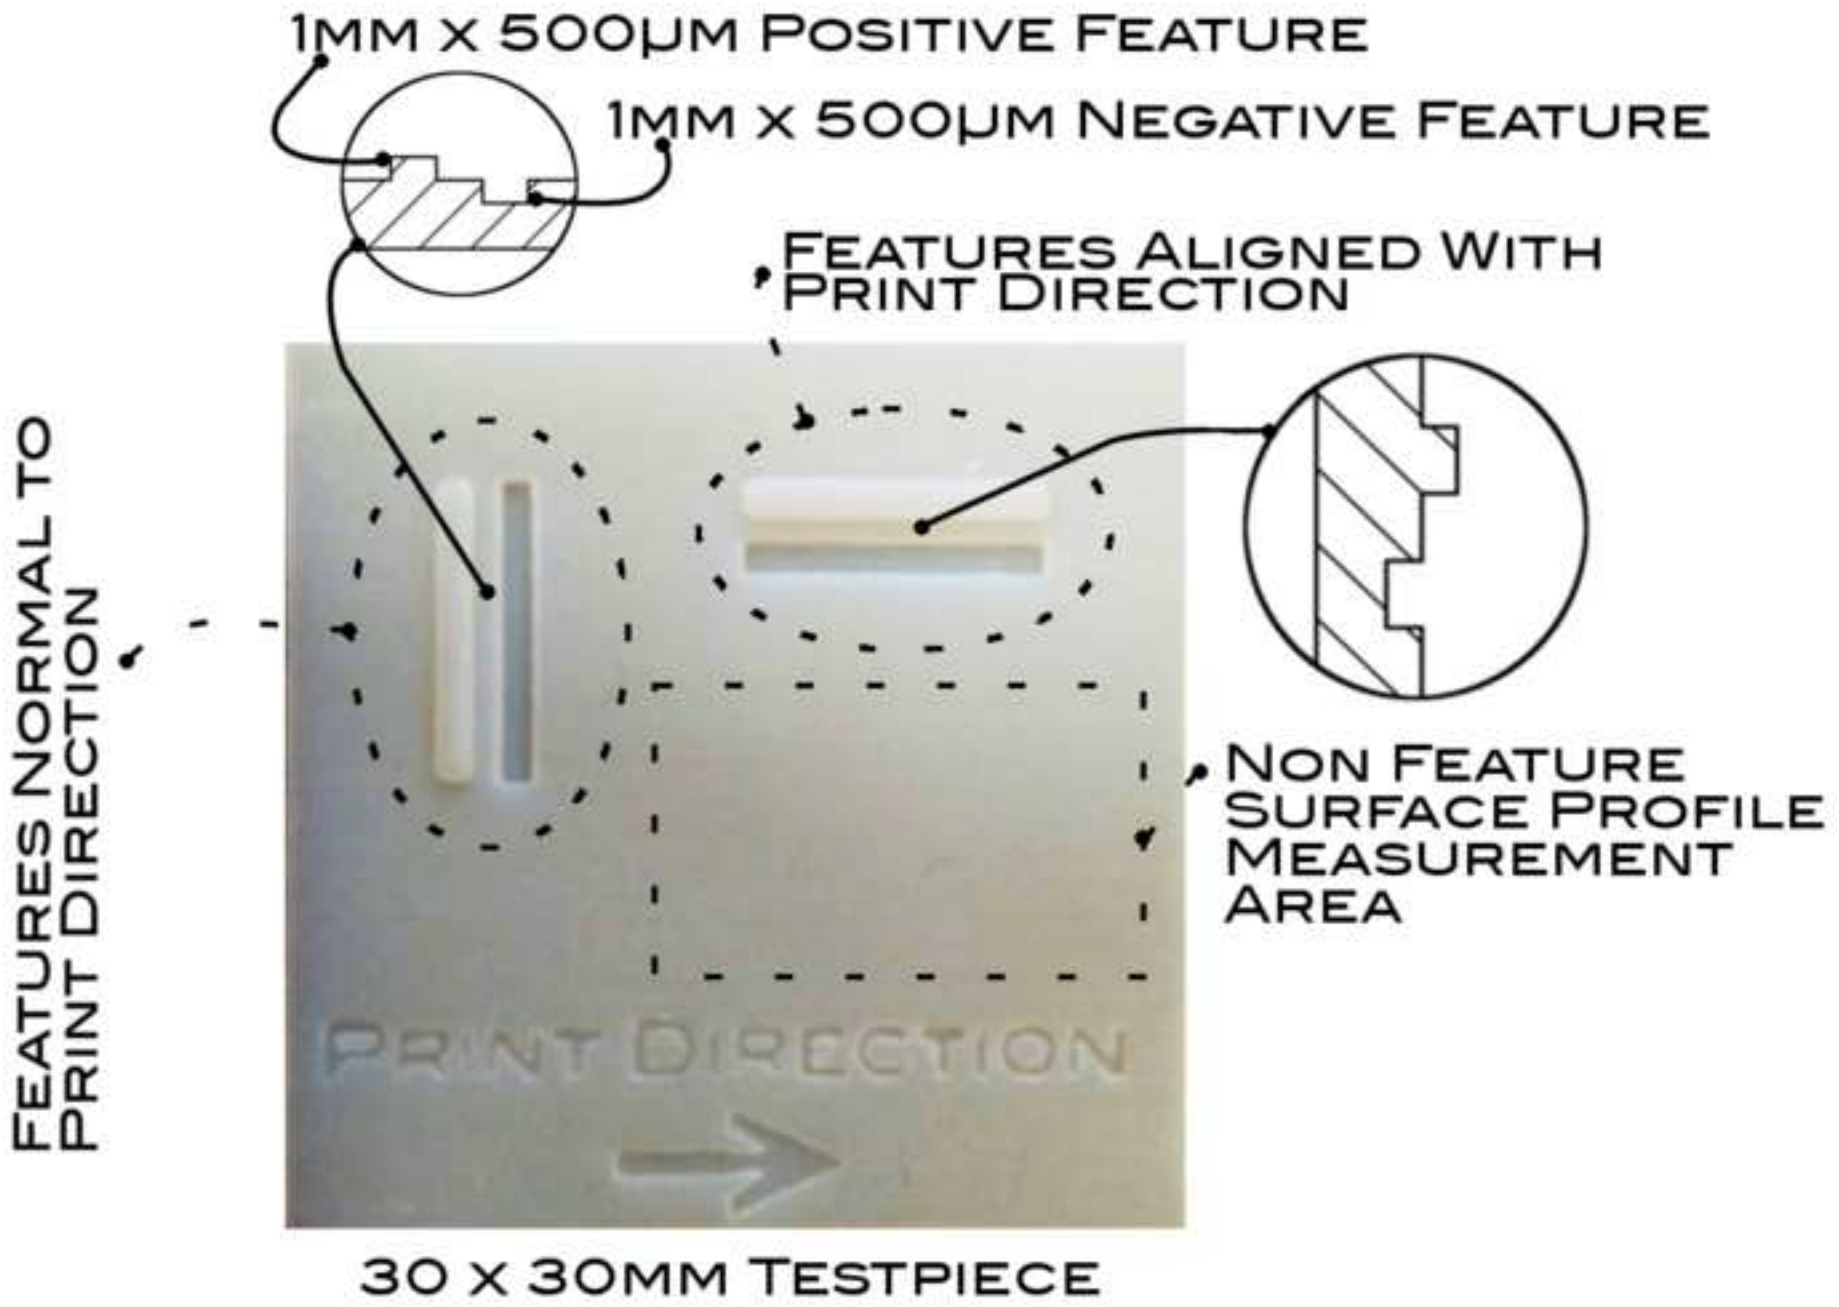


Figure 3

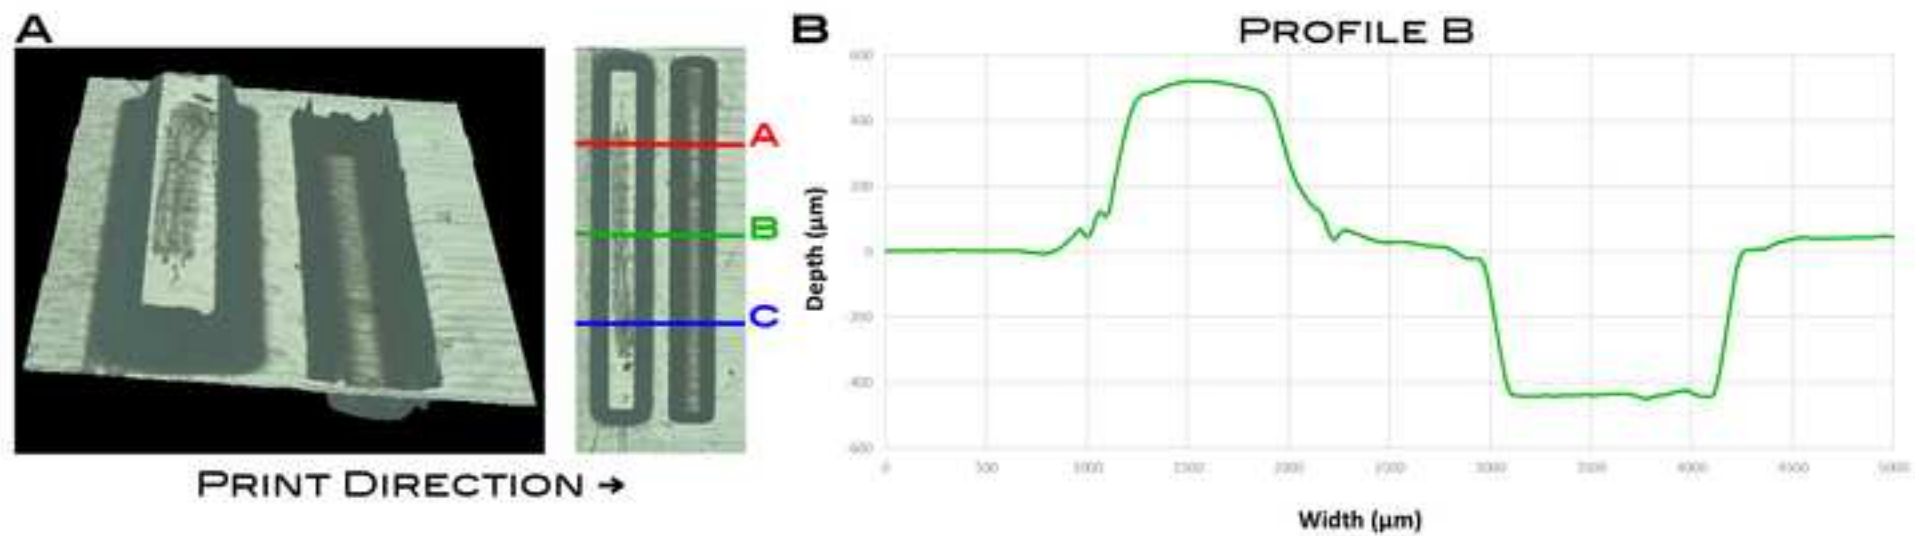


Figure 4

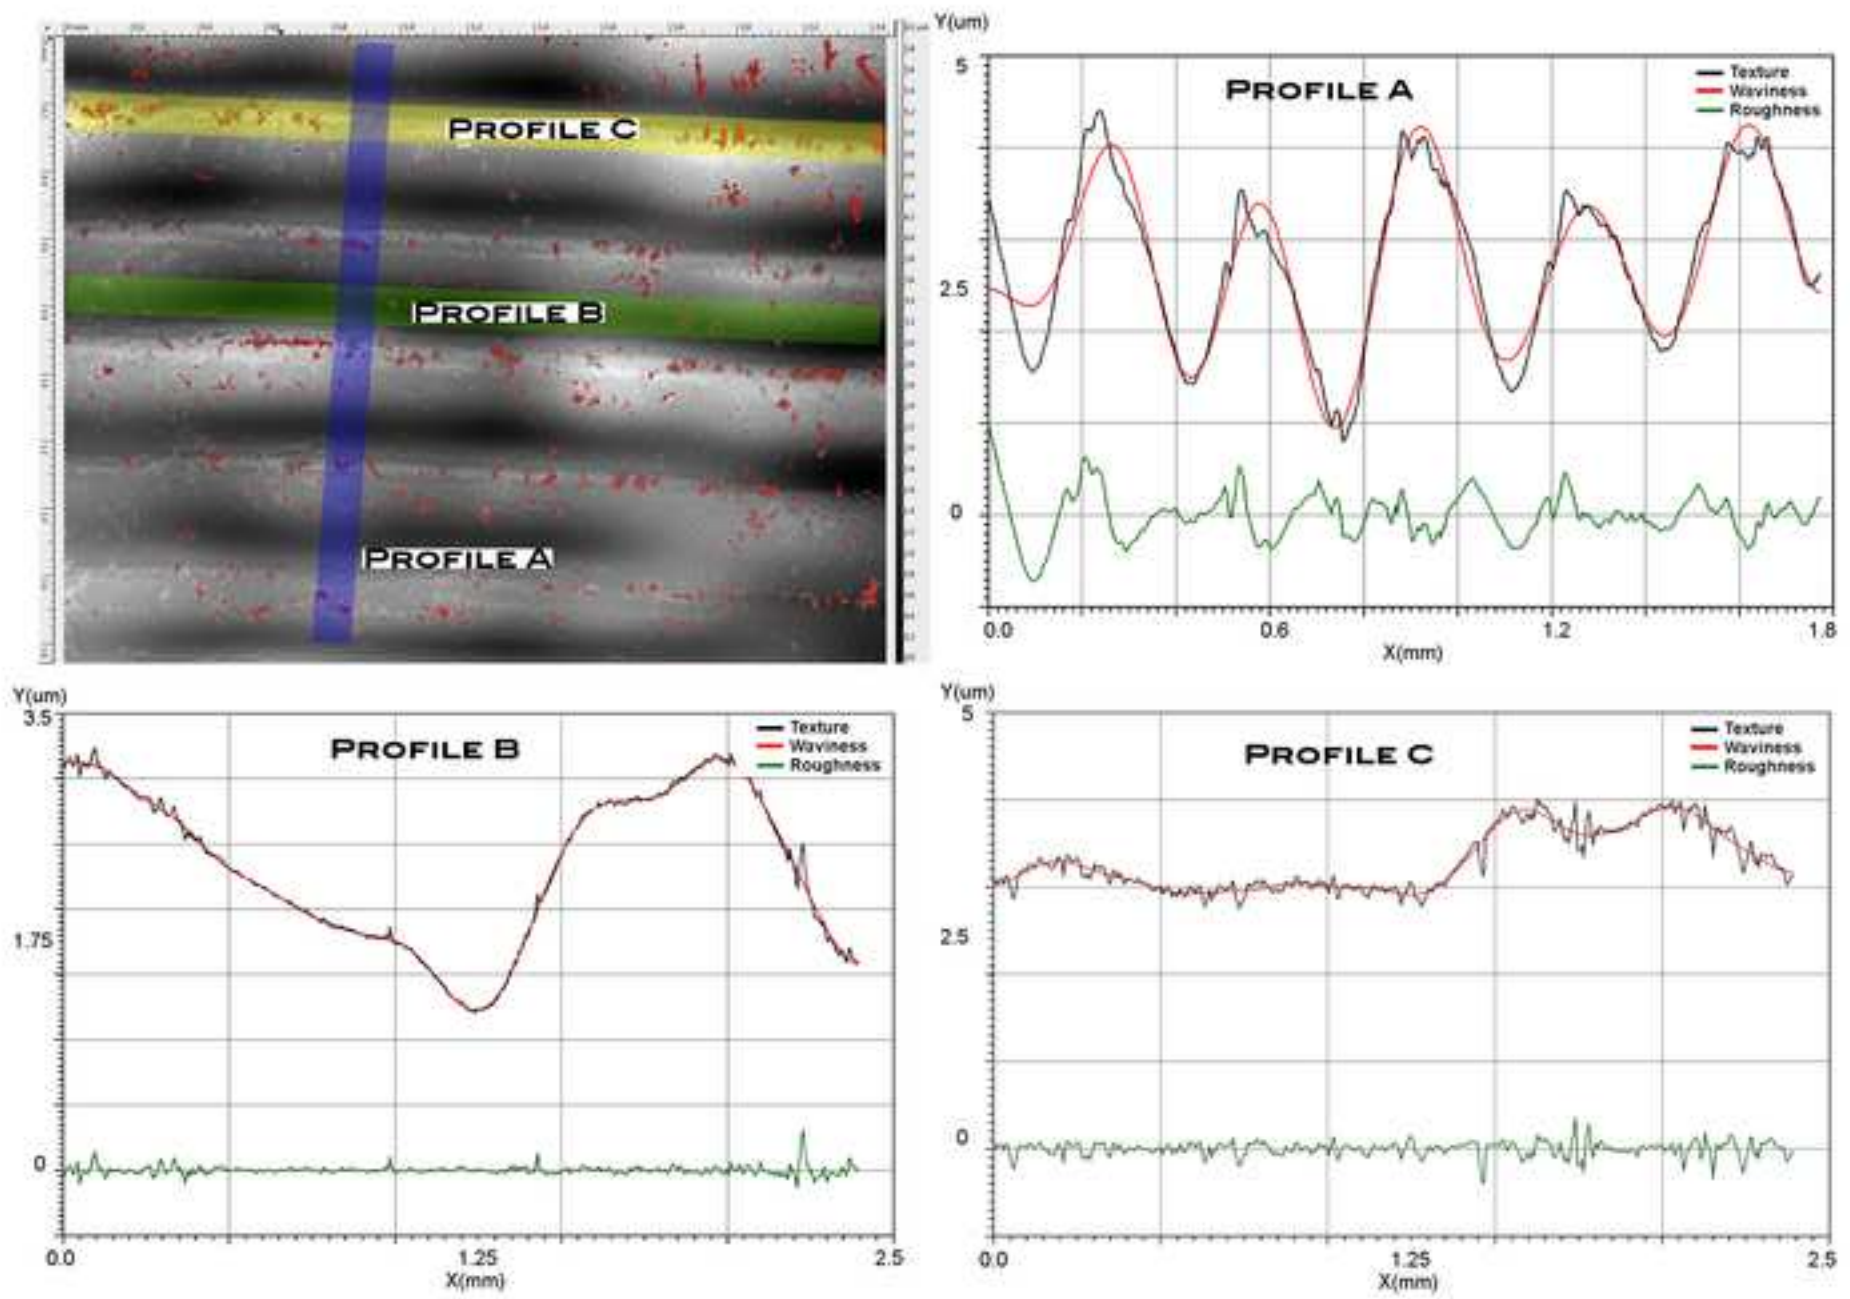


Figure 5

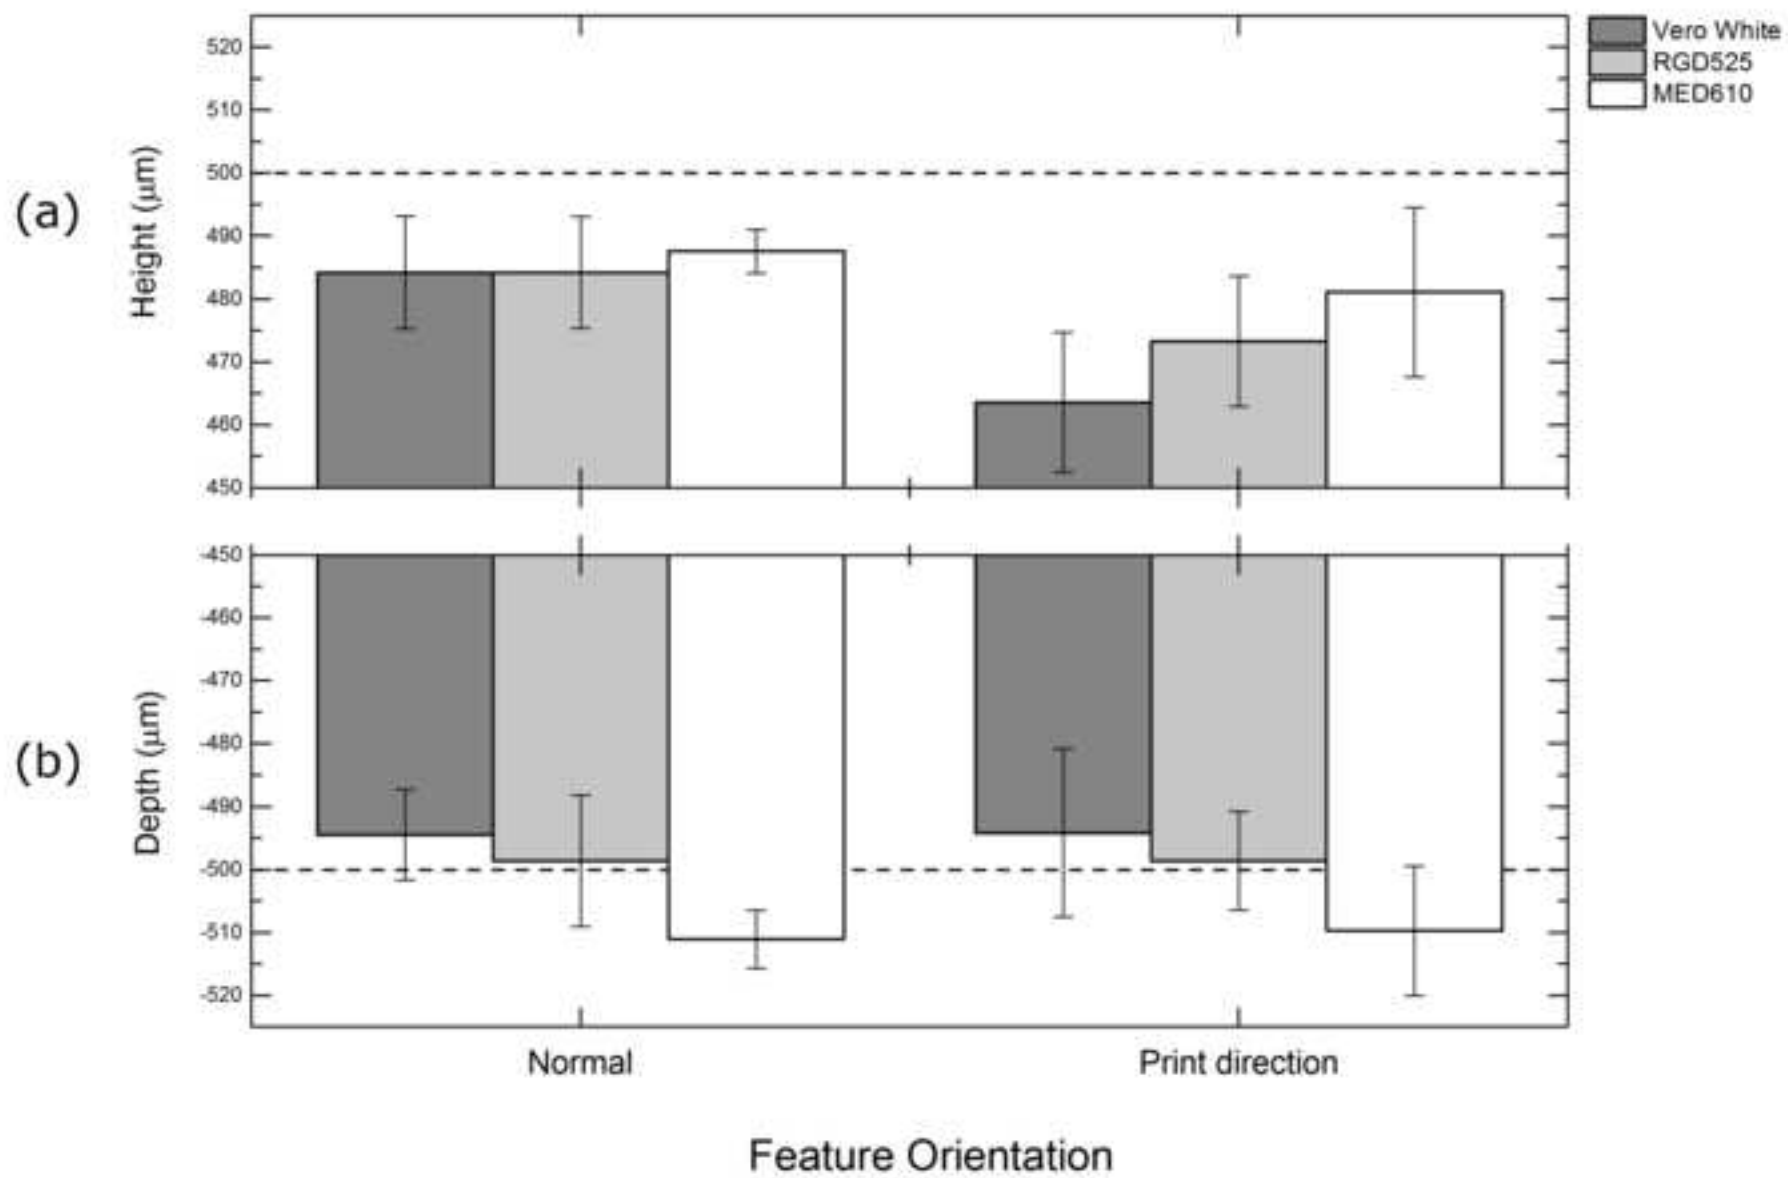


Figure 6

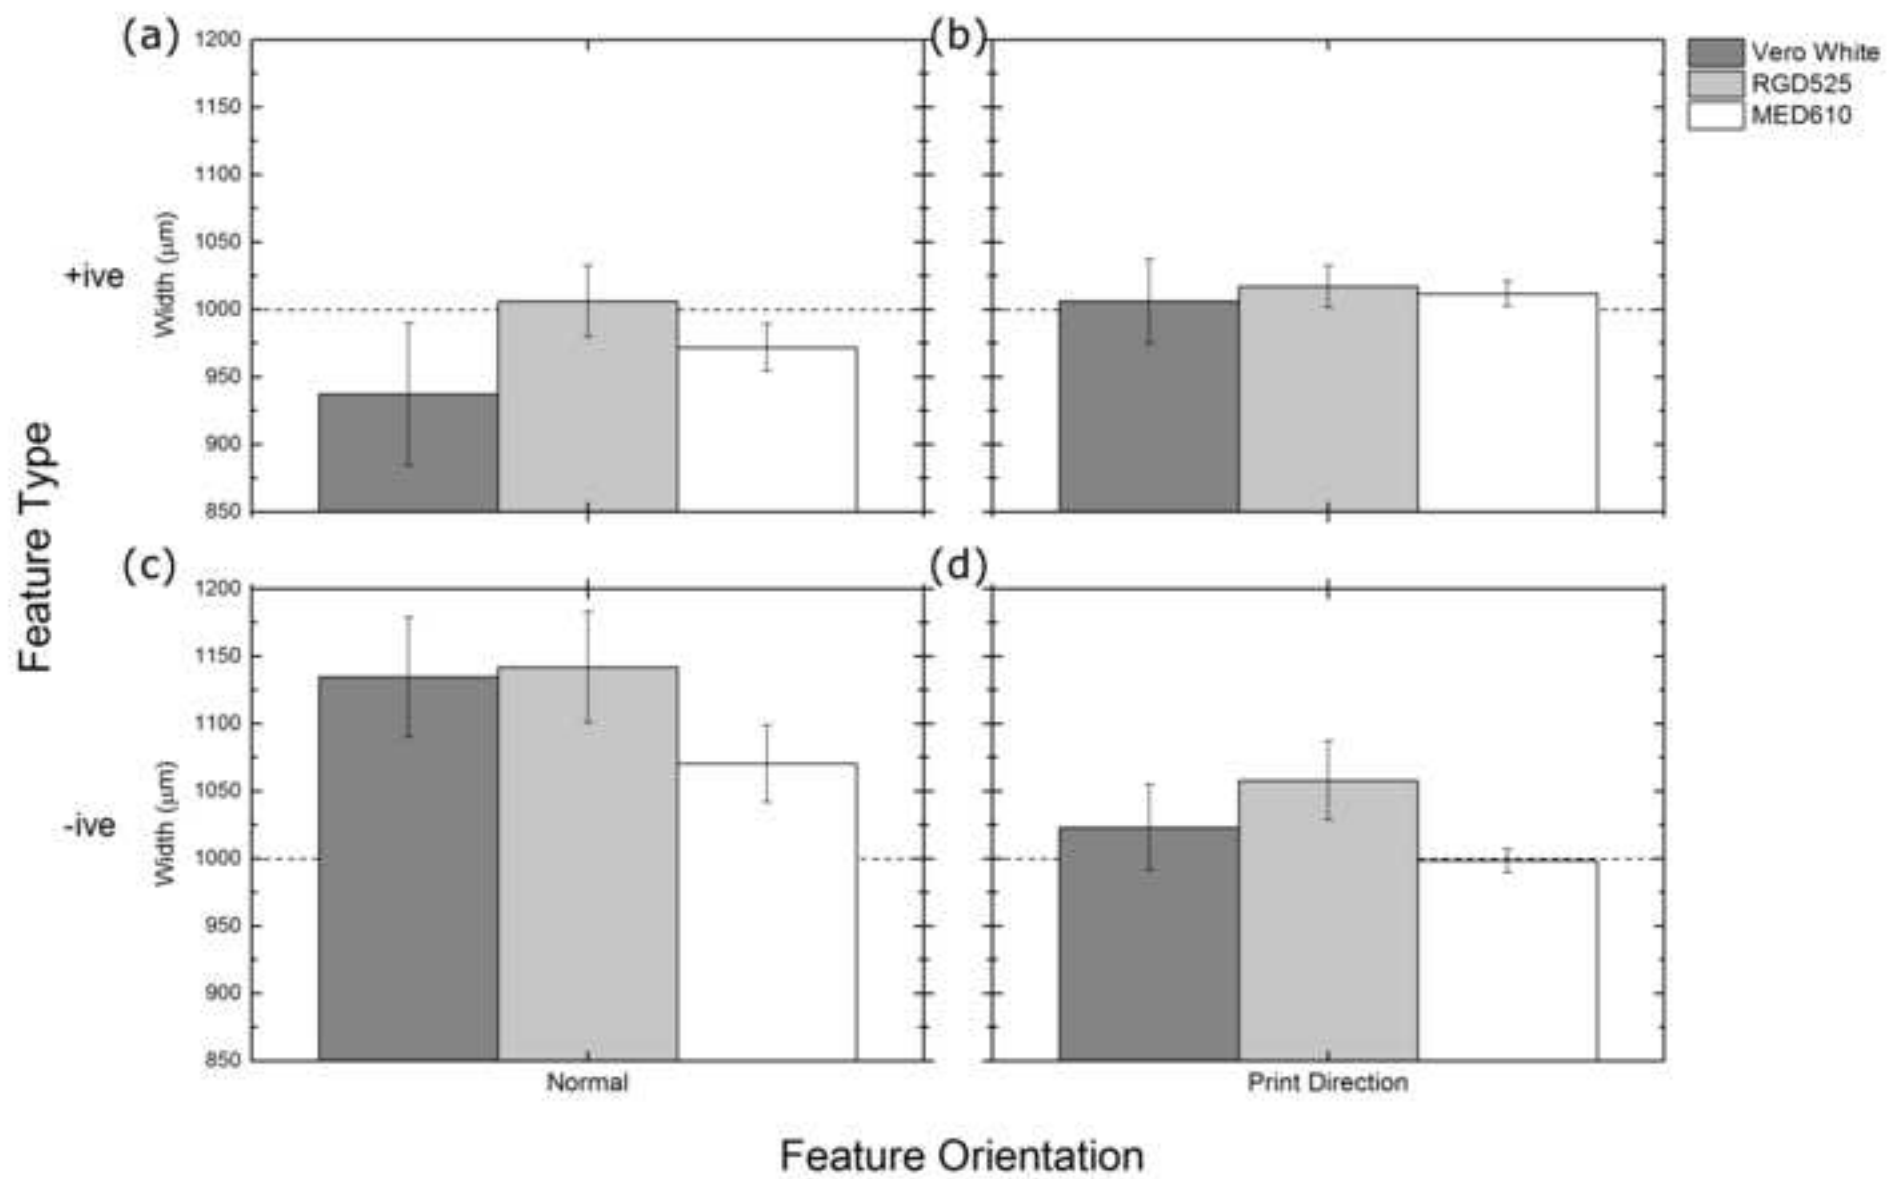


Figure 7

